

Compositional Imaging and Analysis of Late Iron Age Glass from the Broborg Vitriified Hillfort, Sweden

Edward P. Vicenzi^{1,3}, Carolyn I. Pearce², Jamie L. Weaver³, John S. McCloy⁴, Scott Wight³, Thomas Lam¹, Scott Whittaker⁵, Rolf Sjöblom⁶, David K. Peeler², Michael J. Schweiger², and Albert A. Kruger⁷

¹. Museum Conservation Institute, Smithsonian Institution, Suitland, MD, USA

². Pacific Northwest National Laboratory, Richland, WA, USA

³. National Institute of Standards and Technology, Gaithersburg, MD USA

⁴. School of Mechanical and Materials Engineering, Washington State University, Pullman, WA USA

⁵. National Museum of Natural History, Smithsonian Institution, Washington, DC, USA

⁶. Luleå University of Technology, Luleå, Sweden

⁷. Department of Energy, Office of River Protection, Richland, WA USA

Numerous Iron Age hillforts were constructed throughout Europe on high ground to serve ancient settlements [1]. The edifice walls of a small fraction of hillforts were vitriified as a result of high temperature activity, [2]. Swedish hillfort glasses from the Broborg Site near Uppsala, Sweden have recently been proposed as an analogue material to inform long term nuclear waste storage (Fig. 1A) [3]. As part of that effort, a fragment of the Broborg hillfort wall was embedded and polished prior to examination by x-ray methodologies to determine its composition and microstructure (Fig. 1B).

A Bruker M4 Tornado with dual Bruker XFlash 6|60 detectors was used to collect hyperspectral micro-XRF data with a Rh source and a 20 μm (Mo K_{α}) polycapillary optic at two energies: 1) 25 keV/no filter, and 2) 40 keV with a 12.5 μm Al source filter [4]. An FEI Apreo scanning electron microscope (SEM) was used to collect an electron image montage spanning the specimen's polished surface, and electron beam-excited hyperspectral x-ray data was collected using dual Bruker XFlash 6|60 detectors at 15 keV.

Object-scale major element and electron imagery reveals the specimen is comprised of 3 principal chemical phases, an Fe-rich glass (dark), an Fe-poor glass rich in alkalis (milky), and quartz (Fig. 2A,E). Trace element imaging depicts unreacted zircon throughout the sample, Zr and V enrichment in the Fe-rich glass (Fig. 2B-C), and Rb enrichment in the Fe-poor glass (Fig. 2D). A more detailed view of the boundary between the 2 glass zones shows heavily embayed quartz, residual CaAl-silicate zones within the Fe-poor glass, FeMgAl spinel crystallization, and quench-crystallization in the Fe-rich glass (Fig. 3). Major element compositions of the glasses are broadly consistent with previous studies (Table 1) [4,5]. Importantly, the new trace element compositions of the glasses provide an opportunity to test a linkage with the bulk chemistry of lithologies found at Broborg to better understand the ancient melting processes via an elemental ratio comparison.

References:

[1] J McIntosh, Handbook to life in Prehistoric Europe. (Oxford University Press, 2009)

[2] FB Wadsworth et al. J Archaeol. Sci. **67** (2016), p. 7-13

[3] R Sjöblom, H Ecke, & E Brännvall, Intl. J. Sust. Dev. Planning (2013).

[4] Any mention of commercial products is for information only; it does not imply recommendation or endorsement by NIST or DOE.

[5] P Kresten & B Ambrosiani J. Swedish Antiquarian Res. **87** (1992)

[6] JL Weaver et al. Intl. J. Appl. Glass Sci. (*in review*)

Figure 1. A) Oblique aerial view of the Broborg hillfort. B) Sectioned hand specimen image of specimen from vitrified wall.

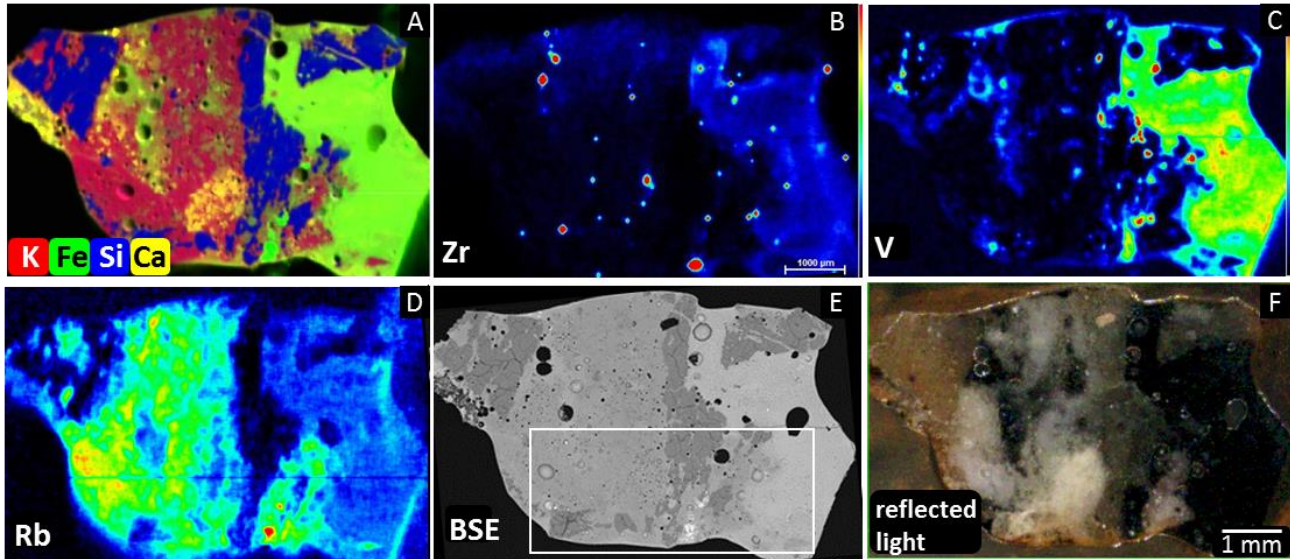
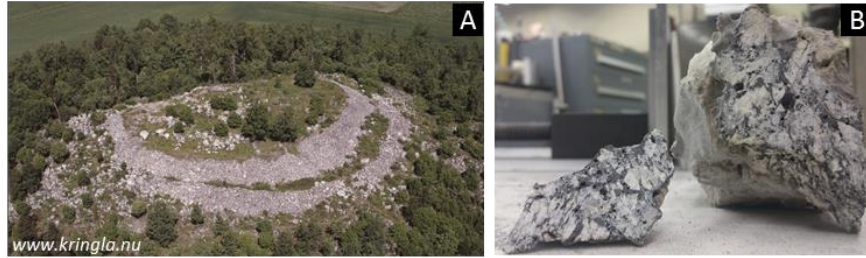


Figure 2. Micro-XRF elemental and electron imagery of vitreous wall fragment. A) Composite x-ray overlay (K K_{α} -red, Fe K_{α} -green, Si K_{α} -blue, Ca K_{α} -yellow). B-D) single element images in rainbow contrast scale Zr K_{α} , Rb K_{α} , and V K_{α} . E) Backscattered electron image (BSE) mosaic, highlighted area enlarge below. F) Reflected light color image.

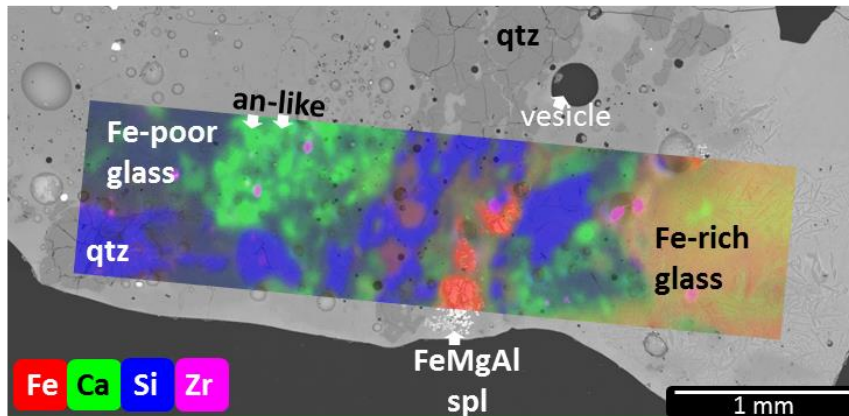


Figure 3. Micro-XRF composite x-ray image superimposed on a BSE image showing the boundary between Fe-rich and -poor glasses [Fe K_{α} -red, Ca K_{α} -green, Si K_{α} -blue, and Zr K_{α} -magenta; quartz (qtz), anorthite (an), and spinel (spl)].

Table 1. Major and trace element analyses of Fe-rich and -poor glasses. Major elements determined by electron beam x-ray analysis (wt %), and trace elements determined by micro-XRF (ppm).

	Fe-rich glass	Fe-poor glass
SiO ₂	54.20	66.65
Al ₂ O ₃	14.69	20.12
CaO	6.42	0.83
MnO	0.31	
FeO*	11.33	
TiO ₂	2.26	
MgO	3.73	
Na ₂ O	3.84	5.18
K ₂ O	2.15	7.18
P ₂ O ₅	0.71	
Total	99.64	99.95
V	279	
Cr	27	
Mn		122
Fe		1962
Co	781	
Ni		20
Zn	362	
Ga	135	
Rb	152	269
Sr	972	449
Y	203	
Zr	1974	
Ba	86	1517