

Recycled Al Reinforced with Oxide Nanoparticles Produced by Stir-Casting Method

A. Santos-Beltrán¹, V. Gallegos-Orozco¹, M. Santos-Beltrán², F.J. Baldenebro-Lopez¹, C.D. Gómez-Esparza², I. Ronquillo-Ornelas¹ and R. Martínez-Sánchez²

¹Universidad Tecnológica de Chihuahua Sur, Km. 3.5 Carr. Chihuahua a Aldama, C.P. 31313. Chihuahua, Chih. México

²Centro de Investigación en Materiales Avanzados (CIMAV), Miguel de Cervantes No. 120, C.P.31109, Chihuahua, Chih., México

Aluminum alloys reinforced with hard nanoparticles named Metal Matrix Nanocomposites (MMNCs) are very attractive in many applications in the industry, this kind of materials exhibit improved mechanical properties with relatively low contents of reinforcement. Automotive and aerospace industries are demanding these composites for critical applications taking into account their low density and high temperature resistance characteristics. MMNC's are materials reinforced with hard particles (e.g. oxides and nitrides) with size ranging from 10 nm to 100 nm. In the present work, nanocomposites based aluminum with hard nanoparticles of TiO₂ and CeO₂ were fabricated by combining two techniques such as mechanical milling and the stir-casting method. Compared to other routes, melt stirring process has some important advantages, e.g., the wide selection of materials, better matrix-particle bonding, easier control of matrix structure, simple and inexpensive processing, flexibility and applicability to large quantity production and excellent productivity for near-net shaped components [1,2]. Nanoparticles and metallic powders, in the weight ratio of Recycled Al/nanoparticles = 3, were separately milled using a Spex ball mill in uncontrolled atmosphere during 2h. The device and milling media used were made from hardened steel. The milling ball to powder weight ratio was set to 5:1. Consolidated samples were added into molten recycled Al using a resistance furnace equipped with a graphite stirring system. Each cylinder was hot extruded in a direct extrusion system at 550 °C. The specimens in both as-milled and as-sintered conditions were studied by scan electron microscopy (SEM) and atomic force microscopy (AFM). The SEM bright-field image (see Fig. 1a) shows the microstructure of the Al-TiO₂ nanocomposite, the inset shows a close up image of the TiO₂ nanoparticles dispersed into the recycled Al matrix; these particles are in the size range of about 80 to 100 nm. Fig. 1b shows the AFM topography image of the Al-TiO₂ composite after the hot extrusion process, the image reveal a homogeneous crystallite size distribution of about 50 to 100 nm. The inset shows the profile of the crystallite.

Fig. 2a shows the SEM bright-field image of the microstructure of the Al-CeO₂ nanocomposite after the hot extrusion process; the image also shows the presence of some fiber-shaped CeAl intermetallic compound. In the inset is clearly observed the CeO₂ nanoparticles dispersed into the recycled Al matrix. The Figure 1b shows the crystallite size distribution where most of these crystallites are below 100 nm in size.

The presence of these hard nanoparticles dispersed into the recycled Al prevents by the pinning effect, the excessive increase of the crystallite during thermo-mechanical extrusion process. The combined effect of hard nanoparticles dispersion and the small crystallite size, improved the mechanical properties of the recycled Al matrix.

References

- [1] C. Suryanarayana, Nasser Al-Aqeeli. Progress in Materials Science 58 - Issue 4 (2013), 383-502.
- [2] H. Abdoli, H. Asgharzadeh, E. Salahi. J. Alloys. Compd 473 (2009), 116–122.

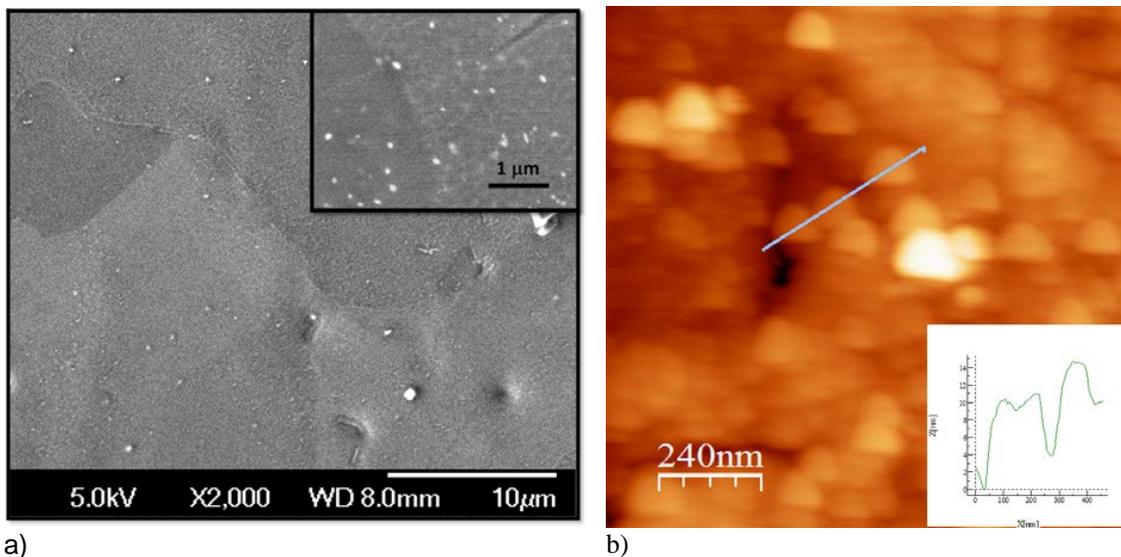


Fig.1. a) SEM bright-field image that shows the Al-TiO₂ microstructure and the inset shows the TiO₂ nanoparticles dispersion into the Al matrix. b) AFM image that shows the crystallite size of the Al-TiO₂ nanocomposite matrix and inset shows the height profile of the crystallite.

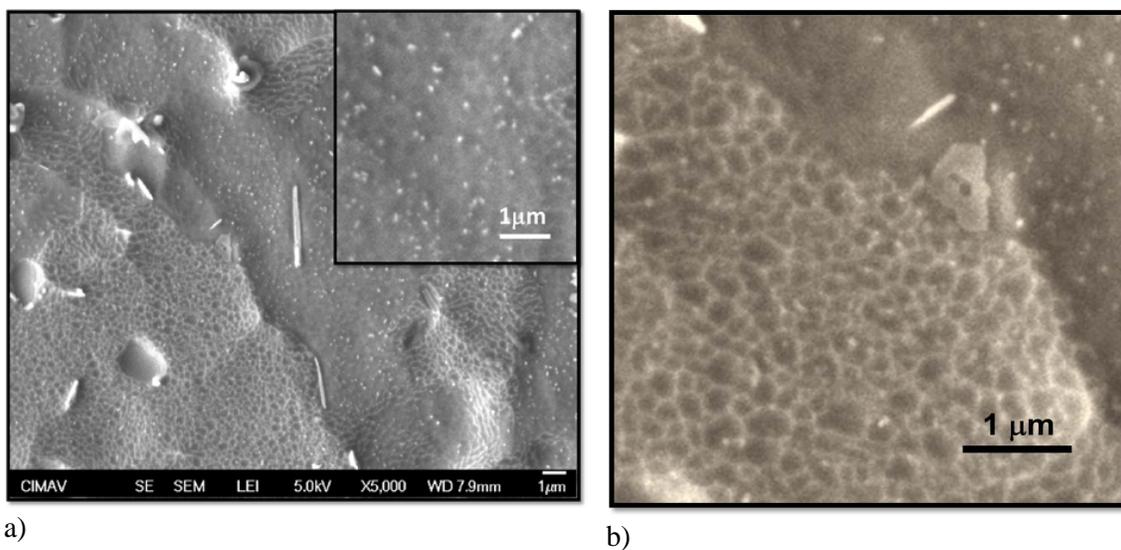


Fig.2. a) Microstructure of the Al-CeO₂ sample (SEM bright-field image), the inset shows a homogeneous nanoparticle dispersion into the Al matrix, b) SEM bright-field image that shows the crystallite size distribution.