

## Grain Boundaries and Anti-Phase Boundaries in $\text{Ba}_{1.015}\text{Zr}_{0.8-x}\text{Ce}_{0.2}\text{Y}_x\text{O}_3$ Proton Conductors

Dan Zhou<sup>1\*</sup>, Wilfried Sigle<sup>1</sup>, Yuanye Huang<sup>1</sup>, Rotraut Merkle<sup>1</sup>, Peter A. van Aken<sup>1</sup> and Joachim Maier<sup>1</sup>

<sup>1</sup> Max Planck Institute for Solid State Research, Stuttgart, Germany.

\* Corresponding author: d.zhou@fkf.mpg.de


Proton conducting ceramics<sup>1</sup> play a key role in clean hydrogen-based electricity generation processes. Protonic ceramic fuel cells (PCFC) are promising due to lower operating temperature and absence of fuel dilution (allowing high fuel utilization). We focus on  $\text{Ba}(\text{Ce},\text{Zr},\text{Y})\text{O}_3$  electrolyte materials owing to its very high bulk proton conductivity and excellent chemical stability at temperatures of 400 ~ 700 °C. However, grain boundaries (GBs) exhibit a blocking character, and both bulk and grain boundary conductivity are very sensitive to the exact cation composition (ratio of Ba to (Ce+Zr+Y)).

We studied the atomic-scale composition and structure of both the bulk and GBs of  $\text{Ba}_{1.015}\text{Zr}_{0.8-x}\text{Ce}_{0.2}\text{Y}_x\text{O}_3$  samples ( $x = 0.05$  and  $0.136$ , sintered by spark plasma sintering (SPS) and annealed at 1500 °C) by aberration-corrected analytical TEM techniques. For both samples, quantitative EDS of GBs showed a decreased density for all elements. The relative concentrations increase for Ba and Y, and decrease for Zr and O. Two types of Ba-rich anti-phase boundaries (APBs), as shown in Figure 1 and Figure 2, were observed in the bulk region by high-angle annular dark-field (HAADF) imaging, which we denote as APB-1 and APB-2. APB-1 has a phase shift of half a  $\{100\}$  plane distance along  $[100]$  direction with BaO planes as the connecting planes. APB-2 has a phase shift between 0 to half a  $\{100\}$  plane distance also along  $[100]$  direction. Different to APB-1, Ce- and Y-rich (Zr,Ce,Y)O planes marked by arrows in Figure 2 are present between the neighboring BaO planes, where Ce shows reduced valence. APB-1s are more frequent for  $x = 0.05$  samples, while  $x = 0.136$  samples show more APB-2s. The importance of APBs to accommodate cation non-stoichiometries will be discussed. More details and their correlation to proton conductivity will be presented [2].


### References:

[1] KD Kreuer, *Annu. Rev. Mater. Res.* **33** (2003), p. 333.

[2] We acknowledge BMBF for funding (ProtoMem, No. 03SF0537C). This project has received funding from the European Union's Horizon 2020 research and innovation programme under grant agreement No. 823717 – ESTEEM3.

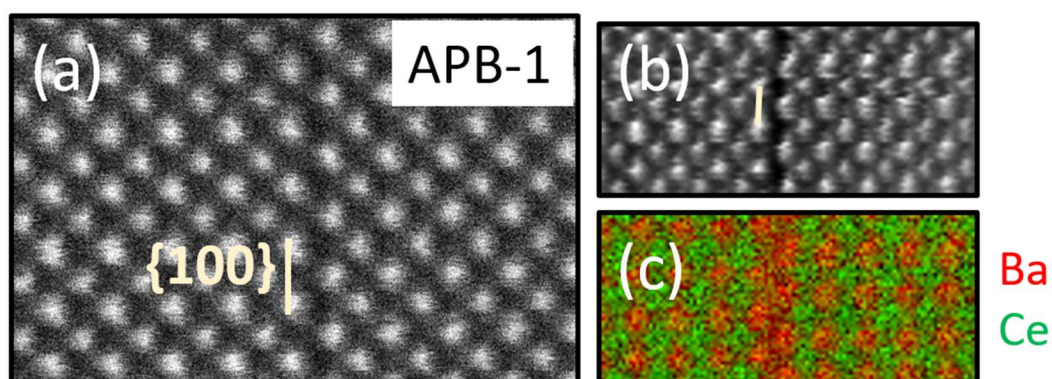

**Figure 1.** (a) HAADF image of APB-1; (b) simultaneously acquired ADF image and (c) EEL spectrum images using Ba-M (red) and Ce-M (green) absorption edges.

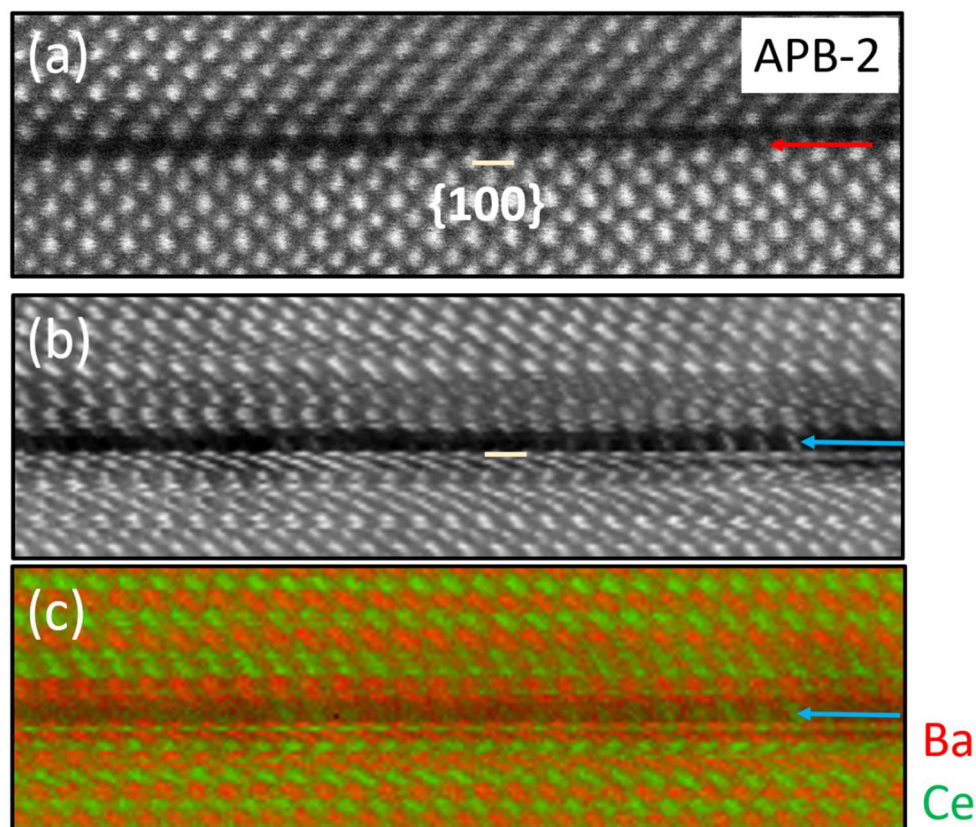

**Figure 2.** (a) HAADF image of APB-2; (b) simultaneously acquired ADF image and (c) EEL spectrum images using Ba-M (red) and Ce-M (green) absorption edges.