

Quantifying Magnetism on the nm Scale: EMCD on Individual FePt Nanoparticles

Sebastian Schneider^{1, 2}, Darius Pohl¹, Stefan Löffler^{3, 4}, Deepa Kasinathan⁵, Jan Ruzs⁶, Peter Schattschneider^{3, 7}, Ludwig Schultz^{1, 2} and Bernd Rellinghaus¹

¹ IFW Dresden, Institute for Metallic Materials, Dresden, Germany

² TU Dresden, Institut für Festkörperphysik, Dresden, Germany

³ Vienna University of Technology, USTEM, Vienna, Austria

⁴ McMaster University, Department of Materials Science and Engineering, Hamilton, Canada

⁵ MPI CPfS, Department Physics of Correlated Matter, Dresden, Germany

⁶ Uppsala University, Department of Physics and Astronomy, Uppsala, Sweden

⁷ Vienna University of Technology, Institute of Solid State Physics, Vienna, Austria

Electron energy-loss magnetic chiral dichroism (EMCD), which is the electron wave analogue of X-ray magnetic circular dichroism (XMCD), offers the possibility to study magnetic properties at the nanoscale in a transmission electron microscope (TEM). The relatively young method of EMCD [1] was already refined to such an extent that it is possible to probe magnetic moments of thin films of a variety of ferromagnets [2, 3, 4]. Meanwhile, these measurements surpass the resolution of XMCD experiments. However, quantitative EMCD measurements are so far only reported on thin films rather than on nanoparticles, which are expected to reveal distinct magnetic properties due to their reduced dimensions and enhanced surface to volume ratio.

We report on EMCD measurements on a single FePt nanoparticle (cf. Figure 1) and compare our experimental findings with simulations. L₁₀ ordered FePt is a particularly interesting material since it offers the highest magneto-crystalline anisotropy among the oxidation-resistant hard magnets [5]. It is therefore a promising materials candidate for future high density magnetic data storage media. L₁₀ ordered FePt nanoparticles on a STO substrate are prepared by sputtering. Prior to the spectroscopic measurements, samples in plan view geometry are subjected to mechanical thinning and grazing incidence Ar⁺ ion milling in order to obtain substrate-free nanoparticles.

The dichroic signals at the Fe L₃ and L₂ edges are expected to amount to no more than 10 % of the absorption edge intensity. Due to these small intensity differences in the electron energy loss (EEL) spectra, a proper microscope alignment, a good reproducibility, a sufficiently stable sample, and a decent signal-to-noise (S/N) ratio pose extreme experimental demands. The experiments were performed on a FEI Titan³ 80-300 microscope equipped with an image C_s corrector. The sample was oriented under three beam conditions with the [001] easy axis of L₁₀ FePt oriented (close to) parallel to the electron beam. Binned-gain acquisition of the EEL spectra was used to optimize the S/N ratio [6]. Particular attention was paid to the analysis of the EEL spectra. A measurement route is presented that allows for the extraction of a dichroic signal from spectra that still suffer from non-optimal S/N ratio. Our experiments are supported by simulations of EEL spectra utilizing the WIEN2k program package [7] in combination with Bloch-wave (BW) methods. These simulations are used to (pre-)determine optimal experimental parameters, that provide for the highest EMCD signals [8, 9]. The experiments reveal a small but reproducible dichroic signal (cf. Figure 2) that agrees well with the results of the theoretical calculations. From these experimental spectra, a ratio of angular to spin moment $m_l/m_s = 0.084 \pm 0.076$ is for the first time quantitatively derived for individual FePt nanoparticles, which agrees well with the XMCD result $m_l/m_s = 0.092$ for a large ensemble of L₁₀ ordered FePt nanoparticles [10] [11,12].

References:

- [1] P. Schattschneider *et al*, *Nature* **441** (2006), p. 486.
 [2] T. Thersleff *et al*, *Scientific Reports* **5** (2015), 13012.
 [3] X. Fu *et al*, *Appl. Phys. Lett.* **107** (2015), 062402.
 [4] D. Song *et al*, *Appl. Phys. Lett.* **107** (2015), 042401.
 [5] J. Lyubina *et al*, *Handbook of Magnetic Materials* **19** (2011), p. 291.
 [6] M. Bosman and V. J. Keast, *Ultramicroscopy* **108** (2008), p. 837.
 [7] K. Schwarz and P. Blaha, *Computational Materials Science* **28** (2003), p. 259.
 [8] S. Löffler and P. Schattschneider, *Ultramicroscopy* **110** (2010), p. 831.
 [9] J. Ruzs, S. Muto and K. Tatsumi, *Ultramicroscopy* **125** (2013), p. 81.
 [10] C. Antoniak *et al*, *Phys. Rev. Lett.* **97** (2006), 117201.
 [11] P. Schattschneider acknowledges financial support by the Austrian Science Fund (FWF) under grant nr. I543-N20.
 [12] S. Löffler acknowledges financial support by the Austrian Science Fund (FWF) under grant nr. J3732-N27.

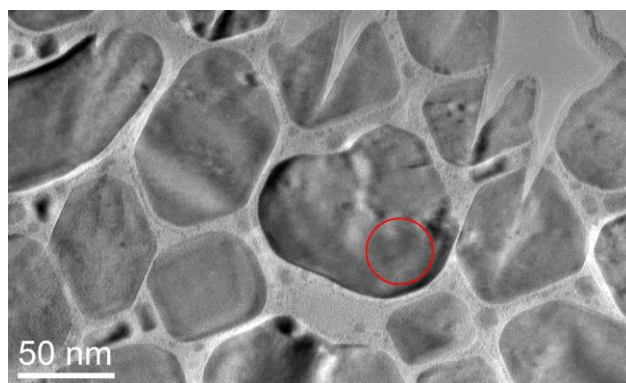


Figure 1. FePt nanoparticles. The area from which the EEL spectra are collected is marked with a red circle.

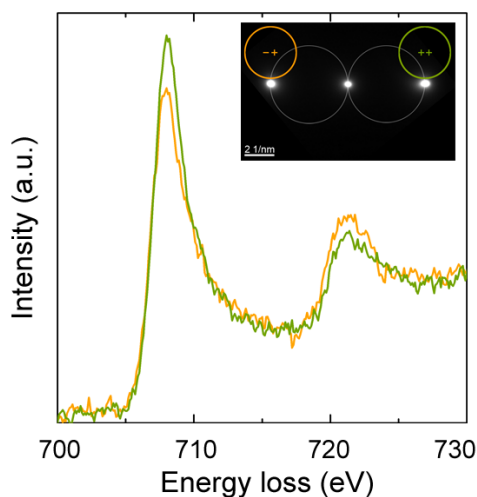


Figure 2. EEL spectra showing a dichroic signal at the Fe $L_{3/2}$ absorption edges. The inset the diffraction pattern under three beam conditions. The areas, from which the EEL spectra are collected, are marked with circles.