

## Analysis of Nitride Layers on ARMCO Pure Iron: The Powder-Pack Nitriding Process

M. Ortiz-Domínguez<sup>1</sup>, O. A. Gómez-Vargas<sup>2</sup>, I. Simón-Marmolejo<sup>1</sup>, M. A. Flores-Rentería<sup>1</sup>, L. E. Martínez-Martínez<sup>1</sup>, A. Cruz-Avilés<sup>1</sup>, M. A. Paredes-Rueda<sup>2</sup>

<sup>1</sup>. Department of Mechanical Engineering, Universidad Autónoma del Estado de Hidalgo-Campus Sahagún, Hidalgo, México.

<sup>2</sup>. Department of Mechanical Engineering, Instituto Tecnológico de Tlalnepantla, EdoMéx, México.


The nitriding of iron and steel is of considerable technological importance, because it can make a pronounced improvement in the fatigue, the wear, and the corrosion resistance of these materials. Nitriding on the surface of ferrous alloys results in the formation of a compound layer of  $\gamma'$ -Fe<sub>4</sub>N<sub>1-x</sub> and  $\epsilon$ -Fe<sub>3</sub>N nitrides or a mixture of  $\gamma'$  and  $\epsilon$  with a nitrogen diffusion zone beneath the nitride layer. The broad range of nitride layer properties needed for different applications requires good control of nitriding process [1-3]. In the powder-pack nitriding process, which is similar to the powder-pack carburizing process, samples are placed in an annealing box with a powder mixture that consists of nitrogen-rich material and an activator. The nitriding temperatures are between 723 K and 823 K, a range in which the nitriding potential is a function of the amount of activator used in the powder mixture. The powder-pack method is a low-cost process particularly suited for the formation of uniform nitride layers on structural alloy components with complex shapes and of various sizes [4-5]. In this study, the microstructure of the  $\gamma'$ -Fe<sub>4</sub>N<sub>1-x</sub> and  $\epsilon$ -Fe<sub>3</sub>N layers formed on an ARMCO pure iron surface have been investigated at different temperatures by the powder-pack process.

The powder-pack nitriding process (Pulnieren©, H. E. F. Durferrit method) was conducted on square commercial samples of ARMCO pure iron with a thickness of 5 mm. Prior to the nitriding process, the samples were ground, polished cleaned at room temperature in H<sub>2</sub>SO<sub>4</sub> for 10 s, and dried and stored in clean-room conditions. The samples were embedded in a closed cylindrical case (AISI 304L stainless steel) having a boron powder mixture inside with an average particle size of 30  $\mu$ m. The pack method in the powder mixture consisting of calcium cyanamide (CaCN<sub>2</sub>, ~24% of N) and calcium silicate (CaSi, ~35 wt.% of the mixture) as an activator. The samples were directly immersed in the powder mixture in another stainless steel cylindrical case. The nitriding temperatures were 723, 773 and 823 K for 2 - 12 h of exposure for each temperature. Nitriding followed after placing the case in a resistance furnace without the use of inert gases. Once treatment was complete, the container was removed from the furnace and slowly cooled to room temperature. The samples were cross-sectioned and resin-embedded for traditional metallographic preparation; the polished samples were etched in a 2% nital solution to observe the nitride layer depths and morphology by SEM and EDS (JEOL JSM-6360 LV at 20 kV). X-Ray Diffraction (XRD) analyses of the layers were carried out with  $2\theta$  varying 20° to 90°, using CuK $\alpha$  radiation and  $\lambda = 1.54 \text{ \AA}$ . Finally, to determine the nitrogen depth profiles, Glow-Discharge Optical Emission Spectroscopy (GDOES) technique utilising a Horiba Jobin Yvon RF GD-Profiller2 operating with an RF source at 20 W and an argon working pressure of 650 Pa, the tests were carried out in the nitrided samples developed at 823 K with 12 h of exposure. Figure 1 shows the cross-sections and the EDS analysis obtained by SEM at the  $\epsilon$ -Fe<sub>3</sub>N/  $\gamma'$ -Fe<sub>4</sub>N<sub>1-x</sub> interphase for the nitrided ARMCO pure iron. The corresponding profile composition revealed maximum nitrogen content on the surface of 25 at% N (Fig. 2). The existence of the  $\epsilon$ -Fe<sub>3</sub>N and  $\gamma'$ -Fe<sub>4</sub>N<sub>1-x</sub> were verified by X-ray diffraction (Fig. 3). The results demonstrate that the morphology of nitrided irons were homogeneous


and flat. Figure 2 shows the profile composition with maximum nitrogen content on the surface of 25 at% N, indicating the development of two nitride layers ( $\epsilon$  -  $\text{Fe}_3\text{N}$  and  $\gamma'$  -  $\text{Fe}_4\text{N}_{1-x}$ ), as confirmed by XRD shown in Figure 3.

#### References:

- [1] H. Du and J. Agren, *Z. Metallkd.* **86** (1995), p. 522.
- [2] J. R. Davis, "Surface Hardening of Steels: Understanding the Basics", 1<sup>st</sup> ed. ASM, Ohio, p. 213.
- [3] K. H. Habig, *Mater. Eng.* **2** (1980) p. 83.
- [4] Z. D. Xiang and P. K. Datta, *Surf. Coat. Technol.* **179** (2004), p. 95.
- [5] K. Y. Li and Z. D. Xiang, *Surf. Coat. Technol.* **204** (2010), p. 2268.

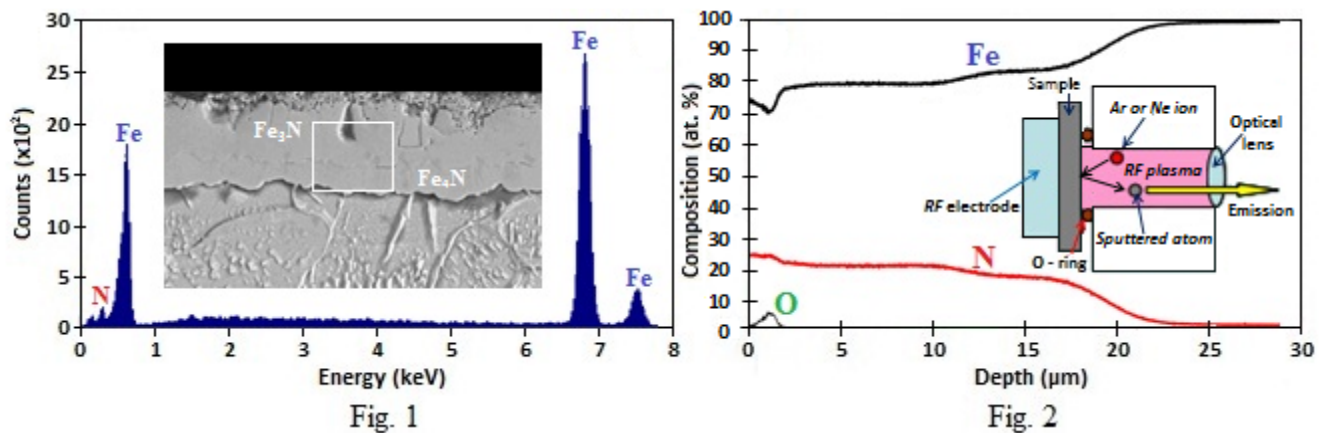

**Figure 1.** Image (SEM) cross-sectional of boro-nitrided ARMCO pure iron showing the produced layers and GDOES (**Figure 2**) spectrum of the elements distribution from the surface to the interior of the nitride  $\gamma'$  -  $\text{Fe}_4\text{N}$  and  $\epsilon$  -  $\text{Fe}_3\text{N}$  layers at 823 K with 12 h.

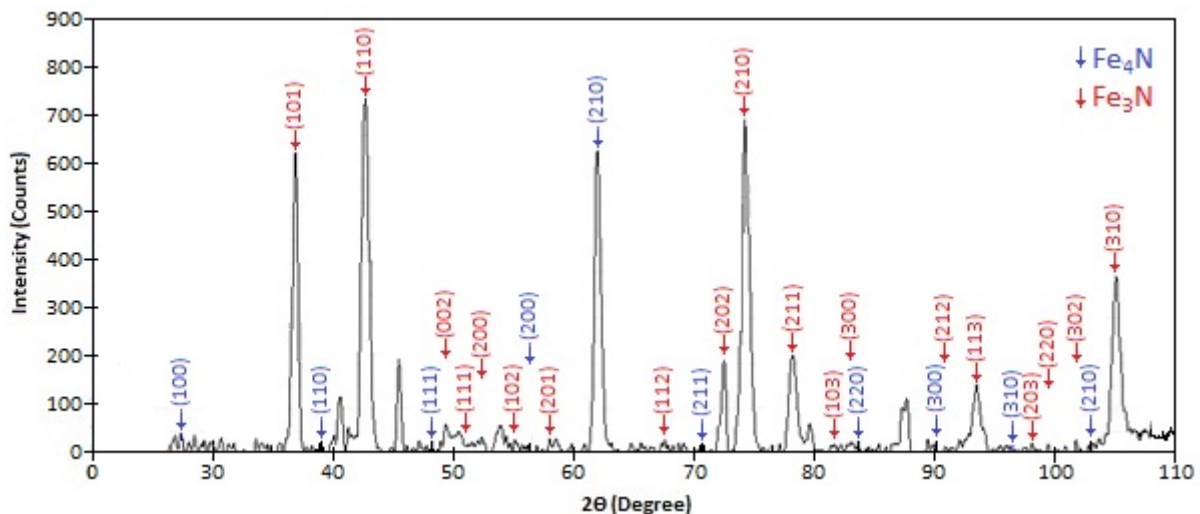

**Figure 3.** XRD from the cross-section of nitride coating, with 823 K for 12 h of exposure time.